

A PAVEMENT RATING SYSTEM FOR HOT-MIX ASPHALT PAVEMENT

HOT-MIX ASPHALT PAVEMENT RATING FORM⁽¹⁾⁽²⁾

STREET/ROUTE/FACILITY NAME: _____

CITY OR COUNTY: _____ DATE: _____

LENGTH OF PROJECT: _____ WIDTH: _____

LOCATION OF SURVEY: _____ WEATHER: _____

PAVEMENT TYPE: _____

NOTES: _____

(Note: a rating of "0" indicates that the distress does not occur)

<u>DISTRESS</u>	<u>RATING</u>	<u>SCORE</u>
Transverse Cracks	0 to 5	_____
Longitudinal Cracks	0 to 5	_____
Alligator Cracks	0 to 10	_____
Shrinkage Cracks	0 to 5	_____
Rutting	0 to 10	_____
Corrugations	0 to 5	_____
Raveling	0 to 5	_____
Shoving or Pushing	0 to 10	_____
Pot Holes	0 to 10	_____
Excess Asphalt/Binder	0 to 10	_____
Polished Aggregate	0 to 5	_____
Deficient Drainage	0 to 10	_____
Overall Riding Quality (0 is excellent; 10 is very poor)	0 to 10	_____

Sum of Distresses = _____

Condition Rating = 100 - Sum of Distresses
= 100 - _____

Condition Rating =

SOURCES:

⁽¹⁾ ASPHALT PAVING DESIGN GUIDE, MAPA

⁽²⁾ INFORMATION SERIES NO. 169 (IS-169), THE ASPHALT INSTITUTE



A PAVEMENT RATING SYSTEM FOR HOT-MIX ASPHALT PAVEMENTS

INTRODUCTION

MAPA commissioned ERES Consultants to evaluate the performance history of Hot-Mix Asphalt (HMA) pavements with and without an aggregate base, and of portland cement concrete pavements on the MnDOT highway system. The results showed that HMA pavements typically provide 40 to 60 years of service life and receive three overlays in that time frame. The first overlay, on average, occurs between 15 and 16 years after construction, but the most common age for an overlay is 18 years. Pcc pavements have a service life similar in length to that of HMA pavements, either full-depth or aggregate base design. Fifty percent of pcc pavements are either overlaid with HMA or otherwise removed from service by the time they reach 20 years of age. Of the remaining fifty percent of pcc pavements, over 50 percent receive major repair work within the first 20 years. See www.asphaltisbest.com for the *Summary of Minnesota Research Findings* more facts on HMA.

While HMA pavements have proven to provide the best driving surface at the lowest life cycle cost, it is important for individuals or agencies with the responsibility of maintaining roadways, streets, parking lots and other hot-mix asphalt (HMA) paved facilities to maintain a logical pavement management system to help decide when to perform routine maintenance, overlay, or reconstruction. Deciding which roads should get first attention is often difficult. One factor complicating the decision is the variety of pavement distress types and treatments – some serious, others rather insignificant.

This publication presents a system that utilizes the experience of an engineer, maintenance superintendent, or foreman to assign a numerical value to each type of pavement distress, taking into account both the extent of distress and its relative seriousness. The sum of these numerical values provides a fairly accurate, though subjective, index of the general condition of the paved surface. As the pavement condition survey is performed on a repeated and timely basis, the index can be useful in setting maintenance priorities. Part 1 of this publication explains the HMA pavement condition rating system. Part 2 contains photographs and descriptions of the different types of distress.



PART 1 – WHERE THE SYSTEM APPLIES

The rating system is intended for agencies, organizations and/or owner not having the benefit of specialized highway engineering experience and without access to conventional testing facilities.

MAKING THE INSPECTION

An effective way of inspecting a pavement is first to drive slowly over the road to get an overall impression of its condition. Then, to make a thorough inspection on foot, making rough notes on the type and extent of distress as one goes along. When the inspection is completed, the rating form is filled out. It may be useful to drive again slowly over the pavement after filling out the rating form. Since the system is based on personal judgment, better results are obtained when two or more experienced individuals independently rate the pavements and the results are averaged.

RATING A ROAD

As mentioned earlier, some distresses affect the performance of a pavement more than others. Under this rating system, the less serious observations are assigned values between zero (0) and five (5). Distress of a more serious nature – those directly related to the strength of the pavement – are rated on a scale of zero (0) to ten (10). A rating of zero (0) means that the pavement is free of that particular type of distress. Part 2 of this publication should be helpful in identifying different types of distresses.

When assigning a rating to a particular type of distress, it is important to consider both its *extent and severity*. For example, a rating of 10 for “rutting” would indicate that it occurs on most or all of the pavement, the ruts are probably deep enough to be a safety hazard (especially during rain), and it is an impediment to traffic at all times. On the other hand, a rating of 1 for “corrugations” would indicate that corrugations, although evident, are not numerous and that at present the distortions are not very large.

After each distress is rated, the individual distress ratings are added. This “Sum of Distresses” is then subtracted from 100, and the result is simply called the “condition rating,” as shown in Figure 1.

HOT-MIX ASPHALT PAVEMENT RATING FORM⁽¹⁾⁽²⁾

STREET/ROUTE/FACILITY NAME: _____

CITY OR COUNTY: _____ DATE: _____

LENGTH OF PROJECT: _____ WIDTH: _____

LOCATION OF SURVEY: _____ WEATHER: _____

PAVEMENT TYPE: _____

NOTES: _____

(Note: a rating of "0" indicates that the distress does not occur)

<u>DISTRESS</u>	<u>RATING</u>	<u>SCORE</u>
Transverse Cracks	0 to 5	_____
Longitudinal Cracks	0 to 5	_____
Alligator Cracks	0 to 10	_____
Shrinkage Cracks.....	0 to 5	_____
Rutting	0 to 10	_____
Corrugations	0 to 5	_____
Raveling	0 to 5	_____
Shoving or Pushing	0 to 10	_____
Pot Holes	0 to 10	_____
Excess Asphalt/Binder	0 to 10	_____
Polished Aggregate	0 to 5	_____
Deficient Drainage	0 to 10	_____
Overall Riding Quality (0 is excellent; 10 is very poor)	0 to 10	_____

Sum of Distresses = _____

Condition Rating = 100 – Sum of Distresses
 = 100 – _____

Condition Rating =

SOURCES:

⁽¹⁾ ASPHALT PAVING DESIGN GUIDE, MAPA

⁽²⁾ INFORMATION SERIES NO. 169 (IS-169), THE ASPHALT INSTITUTE

Figure 1. Hot-Mix Asphalt Pavement Rating Form.



INTERPRETING THE CONDITION RATING

There are two ways that the condition rating can be used. First, as a relative measurement, it provides a rational method for ranking paved streets or facilities according to their condition. Secondly, as an absolute measure, the condition rating provides a general indicator of the type and degree of repair work necessary. As a very general rule, if the condition rating is between 80 and 100, normal maintenance operations such as crack sealing (CRS-2, AC3, crack filling (MnDOT 3719), pot hole repair, or perhaps surface treatment (eg. Fog seal using CSS-1, SS-1, etc.) are usually all that is required. If the condition rating falls below 80, it is likely that an overlay will be necessary. In this event, it may be advisable to contact the Minnesota Asphalt Pavement Association or other qualified engineering personnel for assistance. If the condition rating is below 30, chances are that major reconstruction is necessary, see Figure 2.

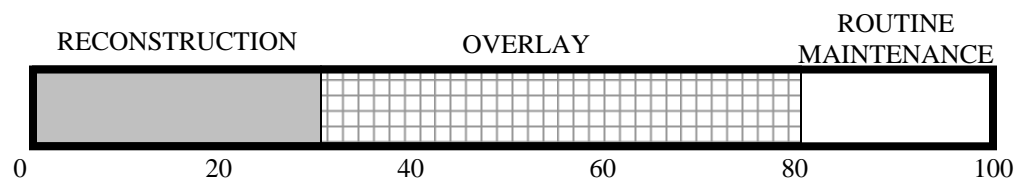


Figure 2. Condition Rating as a General Indicator of Type of Maintenance.

PART 2 – PAVEMENT DISTRESS

CAUSES OF PAVEMENT DISTRESS

Although a detailed discussion of the subject is beyond the scope of this publication, an understanding of the cause of a pavement distress is essential before an attempt is made to remedy it. Similarly, efficient use of a maintenance budget requires that proven methods be used to prevent recurrence of a problem. Accompanying the illustrations of distresses that follow, there is a brief statement of their usual cause and the suggested means of repair. If more detailed assistance is needed in determining either the cause of a distress or the proper method of its repair, it may be advisable to contact MAPA.

Other resources are:

- Distress Identification Manual for the Long-Term Pavement Performance Project, U.S. Department of Transportation, Federal Highway Administration, Publication No. FHWA-RD-03-031, June 2003.
- Mn/DOT Distress Identification Manual, Minnesota Department of Transportation, Office of Materials and Road Research, Pavement Management Unit, February 2003.
- Crack Sealing Bituminous Pavements in Minnesota, MnDOT Report No. 92-03, 1992.
- Asphalt Pavement Maintenance Field Guide, Manual Number 2001-05 Rev., January 2002.
- Flexible Pavement Distress Manual, Local Road Research Board.
- Surface Condition Rating System, NCHRP Project 10-9, Civil and Mineral Engineering Department, University of Minnesota, January 1973.
- Full-Depth Asphalt Patching, Asphalt Institute, CL-19.
- Overlays and Pavement Rehabilitation, Asphalt Institute, MS-17.
- Minnesota Asphalt Pavement Association Web Site: www.asphaltisbest.com, “Resources” tab.

TRANSVERSE CRACK: A crack that follows a course approximately at right angles to the pavement centerline. This frequently is caused by movement in the pavement beneath the HMA layer (reflection cracking). It can also result from stresses induced by low-temperature contraction of the pavement. It may require sealing or filling with asphalt material. At a later date, this may be followed by an overlay (eg. tight blade, paver lay) or mill and fill over the entire surface. *Photo courtesy of the US DOT and National Center for Asphalt Technology (NCAT).*



LONGITUDINAL CRACK: A crack that follows a course approximately parallel to the centerline.



This usually results from a weak joint between paving lanes. These cracks can also result from earth movements, particularly on embankments. Two closely-spaced longitudinal cracks in the wheel path usually indicate bending stress induced by rutting. Longitudinal cracks can also occur as a result of movement in the pavement beneath the HMA layer (reflection cracking or stripping). For repair, see "Transverse Crack." *Photo courtesy of the US DOT and NCAT.*

ALLIGATOR CRACKING: Interconnected cracks forming a series of small polygons, the pattern resembles an alligator's skin. It is caused by excessive deflection of the surface over unstable pavement base or subgrade layers that leads to fatigue failure. The unstable support usually is the result of saturated layer or layers or an unstable pavement design. It requires deep patching with HMA.



SHRINKAGE CRACKS: Interconnected cracks forming a series of large polygons, usually having sharp angles at the corners. It is caused by volume change in the base or subgrade. It requires monitoring of the hairline cracks, crack sealing, or fog treatment with asphalt material possibly followed by a surface treatment over the entire surface. *Photo courtesy of MnDOT.*



It is caused by volume change in the base or subgrade. It requires monitoring of the hairline cracks, crack sealing, or fog treatment with asphalt material possibly followed by a surface treatment over the entire surface. *Photo courtesy of MnDOT.*

RUTTING: Longitudinal depressions that form under traffic in the wheel paths and have a minimum length of at least 20 ft. It is caused by consolidation or lateral movement under traffic in one or more of the underlying courses, or by displacement in the surface layer itself. Ruts should be filled with HMA (tight-blade) to restore proper cross-section. This should be followed by a thin overlay of HMA. *Photo courtesy of Asphalt Institute.*



CORRUGATIONS: Transverse undulations at regular intervals in the surface of the pavement consisting of alternate, closely-spaced valleys and crests. It is caused by a lack of stability in the surface layers and requires repair before resurfacing. If the corrugated pavement has an aggregate base with a thick surfaced treatment, a satisfactory corrective measure is to mill off the surface, and replace with HMA. If the pavement has more than three inches (3") of HMA, shallow corrugations can be removed with a pavement milling machine, better known as "cold milling." This can be followed with a surface treatment or HMA overlay. *Photo courtesy of the US DOT and NCAT.*



RAVELING: The progressive disintegration from the surface downward, or edges inward by the dislodgement of aggregate particles. It is caused by the original mix type, compaction capability during construction, construction during wet or cold weather, or overheating of the asphalt mix. It usually requires a surface treatment of some type. *Photo courtesy of LRRB.*



SHOVING: Lateral displacement of paving material due to traffic, generally resulting in the bulging of the surface. It is caused by lack of stability in the subgrade, base, or surface layers. It requires the removal of the affected area followed by deep patching with HMA. *Photo courtesy of FHWA.*



POT HOLES: Bowl-shaped holes of varying sizes in the pavement, often resulting from the progressive deterioration of other distresses such as alligator cracking. It usually is caused by a combination of weaknesses in the pavement for the given traffic resulting from insufficient HMA surface thickness, too many or too few fines, and/or poor drainage. It requires removal of the affected area followed by deep patching with HMA.




EXCESS ASPHALT/BINDER (BLEEDING): Free asphalt/binder on the surface of the pavement.



It is caused by too much asphalt/binder in one or more of the surface layers. In many cases, bleeding can be corrected by repeated applications of hot sand, hot screenings, or hot rock screenings to blot up the excess asphalt/binder. Sometimes, when bleeding is light, a plant mixed surface treatment or an aggregate seal coat using absorptive aggregate is the only treatment needed. In rare instances of heavily over-asphalted surfaces, the surface should be completely removed and replaced with HMA.

POLISHED AGGREGATE: Aggregates in the surface of the pavement that have been polished smooth. It is caused by naturally smooth, non-crushed gravels and/or crushed rock that wears down quickly under action of traffic. It requires covering the surface with a HMA treatment that has good frictional characteristics. *Photo courtesy of FHWA.*

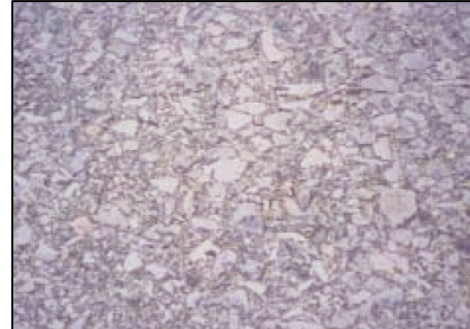

DEFICIENT DRAINAGE: Drainage problems may be considered in two categories: surface and subsurface. Proper surface drainage efficiently removes runoff from the pavement and the nearby ground.



Standing water on the pavement or in the side ditches indicates a drainage deficiency. Proper subsurface drainage keeps groundwater from the pavement structure. Two indicators of deficient subsurface drainage are 1) constant water in the side ditch, possibly with cat tails growing, and in the absence of precipitation, or 2) alligator cracking with moisture in the cracks.

HOT-MIX ASPHALT PAVEMENT RATING FORM⁽¹⁾⁽²⁾

STREET/ROUTE/FACILITY NAME: _____

CITY OR COUNTY: _____ DATE: _____

LENGTH OF PROJECT: _____ WIDTH: _____

LOCATION OF SURVEY: _____ WEATHER: _____

PAVEMENT TYPE: _____

NOTES: _____

(Note: a rating of "0" indicates that the distress does not occur)

<u>DISTRESS</u>	<u>RATING</u>	<u>SCORE</u>
Transverse Cracks	0 to 5	_____
Longitudinal Cracks	0 to 5	_____
Alligator Cracks	0 to 10	_____
Shrinkage Cracks.....	0 to 5	_____
Rutting	0 to 10	_____
Corrugations	0 to 5	_____
Raveling	0 to 5	_____
Shoving or Pushing	0 to 10	_____
Pot Holes	0 to 10	_____
Excess Asphalt/Binder	0 to 10	_____
Polished Aggregate	0 to 5	_____
Deficient Drainage	0 to 10	_____
Overall Riding Quality (0 is excellent; 10 is very poor)	0 to 10	_____

Sum of Distresses = _____

Condition Rating = 100 – Sum of Distresses
 = 100 – _____

Condition Rating =

SOURCES:

⁽¹⁾ ASPHALT PAVING DESIGN GUIDE, MAPA

⁽²⁾ INFORMATION SERIES NO. 169 (IS-169), THE ASPHALT INSTITUTE



MAPA'S CONTRACTOR MEMBERS

Anderson Brothers Construction Co.	Knife River Materials	Rum River Contracting Company
Barton Enterprises, Inc.	M.R. Paving & Excavating, Inc.	Shamrock Enterprises of Rochester LLC
Bemidji Bituminous, Inc.	Mark Sand & Gravel Company	Straight River Asphalt LLC
Bituminous Paving, Inc.	McNamara Contracting, Inc.	T.A. Schifsky & Sons, Inc.
Bituminous Roadways, Inc.	Mesabi Bituminous, Inc.	Tower Asphalt, Inc.
Commercial Asphalt Company	Midwest Asphalt Corporation	Tri-City Paving, Inc.
DMJ Corporation	North Valley, Inc.	Ulland Brothers, Inc.
Duininck Bros., Inc.	Northland Paving, LLC	Valley Paving, Inc.
FPI Paving Contractors, Inc.	Northwest Asphalt, Inc.	Wm. Mueller & Sons, Inc.
Hardrives, Inc.	Pine Bend Paving, Inc.	W W Blacktopping, Inc.
Hawkinson Construction	Plehal Blacktopping, Inc.	
Knife River - North Central	River Bend Asphalt Company	

MAPA'S ASSOCIATE MEMBERS

Accurate Test Systems, Inc.	Fabyanske, Westra, Hart & Thomson, P.A.	Olson & Price, Ltd.
Aggregate Industries	FC Stone	Partek Supply, Inc.
American Agency, Inc.	T.C. Field & Company	Prinsco, Inc.
American Engineering Testing, Inc.	Five Star Industries, Inc.	R & G Construction Company
American Surface Lines, LLC	Flint Hills Resources, LP	RDO Equipment Co.
Anderson Industrial Scales, Inc.	Gencor Industries, Inc.	Ritchie Bros. Auctioneers (America) Inc.
Antigo Construction, Inc.	Grant Thornton LLP	RJ Ahmann Company
Area Lakes Testing	Hayden-Murphy Equipment Co., Inc.	Road Fabrics, Inc.
Arr-Maz Custom Chemicals	Highway Technologies	Road Machinery & Supplies Co.
Asphalt Surface Technologies Corp.	HTIF Cameron Filters	Roadtec, Inc.
Astleford International Trucks	Humboldt Manufacturing	Ruffridge-Johnson Equipment Co., Inc.
Bomag Americas	I.R.A.Y. Auction	RB Scott Company, Inc.
Braun Intertec Corporation	Independent Testing Technologies, Inc.	SPC Engineering & Testing, Inc.
Brock White Company LLC	Inspec, Inc.	STORK Twin City Testing Corporation
Carlson Paving Products, Inc.	Interstate Engineering, Inc.	Swanston Equipment Companies
Caterpillar Paving Products Inc.	Intex Corporation	Sweeney Brothers Tractor, Inc.
Cedarleaf, Cedarleaf & Cedarleaf, Inc.	J-CRAFT by TBEI	Testquip, LLC
Century Fence Co.	Johnson Crushing, Inc.	TexPar Energy, LLC
Certainteed Corporation	Klein Agency, Inc.	Tricon Metals & Services, Inc.
Citicapital Construction Equipment Finance	Kraemer Mining & Materials, Inc.	Tri-County Aggregate, Inc.
Clarence Richard Company	Laser Control, Inc.	Tri-State Aggregate Machinery
Cobb Strecker Dunphy & Zimmermann Inc.	Leonard, Street & Deinard, P.A.	Troxler Electronic Lab., Inc.
Construction Bulletin	L.G. Everist, Inc.	Ulteig Engineers, Inc.
Crysteel Truck Equipment, Inc.	Lubrication Technologies, Inc.	Unique Paving Materials Corporation
Custom Welding & Metal Fab, Inc.	Marathon Petroleum Company LLC	Vance Brothers
Dahl Trucking	Martin Marietta Aggregates	Volvo Construction Equipment
Dillman Equipment	Max Steining, Inc.	Wenck Associates, Inc.
J.D. Donovan, Inc.	Minnesota Petroleum Marketers Assoc.	Wheeler Lumber LLC
Dresser Trap Rock Company	Minnesota Trucking Association	Widseth Smith Nolting
Erickson Engineering Company	Murphy Oil USA, Inc.	Ziegler, Inc.
Esch Construction Supply, Inc.	Northern Balance & Scale	
Ess Brothers & Sons, Inc.	Northwest Process Equipment, Inc.	
EverCore LLC		

CONTACT MAPA AT: 900 Long Lake Road, Suite 100, New Brighton, MN 55112

Phone: (651) 636-4666 • Fax: (651) 636-4790 • Web: www.asphaltisbest.com

